

Optical properties of pyrochlore oxide $Pb_2Ru_2O_{7-\delta}$

P. Zheng, N. L. Wang, and J. L. Luo

*Institute of Physics and Center for Condensed Matter Physics,
Chinese Academy of Sciences, P. O. Box 603, Beijing 100080, P. R. China*

R. Jin and D. Mandrus

Condensed Matter Sciences Division, Oak Ridge National Laboratory, Oak Ridge, TN 37831

We present optical conductivity spectra for $Pb_2Ru_2O_{7-\delta}$ single crystal at different temperatures. Among reported pyrochlore ruthenates, this compound exhibits metallic behavior in a wide temperature range and has the least resistivity. At low frequencies, the optical spectra show typical Drude responses, but with a knee feature around 1000 cm^{-1} . Above 20000 cm^{-1} , a broad absorption feature is observed. Our analysis suggests that the low frequency responses can be understood from two Drude components arising from the partially filled Ru t_{2g} bands with different plasma frequencies and scattering rates. The high frequency broad absorption may be contributed by two interband transitions: from occupied Ru t_{2g} states to empty e_g bands and from the fully filled O 2p bands to unoccupied Ru t_{2g} states.

PACS numbers: 78.20.-e, 78.30.-i, 72.80.Ga

Pyrochlore compounds with general formula $A_2B_2O_7$ are face-centered-cubic oxides with space group $Fd\bar{3}m$ (A and B are cations). While B cation is six-fold coordinated and locates at the center of the distorted octahedra formed by corner O ions denoted as O(1), A cation is eight-fold coordinated with six O(1) and two other oxygen ions O(2). The BO_6 octahedra are corner-sharing and compose a three-dimensional tetrahedral network, namely, the pyrochlore lattice. Intensive investigations of pyrochlore oxides have revealed a remarkable range of interesting and complex phenomena including colossal magnetoresistive effect, heavy Fermion behavior, superconductivity, spin ice, spin glass and metal-insulator transition by selecting different A and B cations. Among those phenomena, the metal-insulator(MI) transition of ruthenates (B = Ru) is unexpected and has thus attracted much attention^{1,2,3,4,5,6,7,8}.

In general, the electron correlation degree of 4d materials is smaller than that of 3d materials and is thought to be within the intermediate-coupling regime. For pyrochlore ruthenates, $A_2Ru_2O_7$, the electrical properties show systematic change from a Mott insulator to a metal depending on A cation. For example, $Y_2Ru_2O_7$ is an insulator²; $Tl_2Ru_2O_7$ exhibits a metal-insulator transition at 120 K,³ accompanied with a structural change from cubic to orthorhombic symmetry. Both $Pb_2Ru_2O_{7-\delta}$ ⁴ and $Bi_2Ru_2O_7$ ⁵ remain metallic electrical properties from room temperature to lowest measured temperature. It is found that metallic $A_2Ru_2O_7$ has a greater Ru-O-Ru bond angle than those of insulating compounds⁹. The angle is affected by A cation. There are two possible roles of A cation: (1) modifying the Ru 4d band width through the change of Ru-O-Ru bond angle⁸, and (2) contributing some states to the total states near the Fermi level^{1,6}.

Optical spectroscopy is a powerful tool to probe the electronic structure and charge dynamics of a material. Several optical measurements have been performed on

$A_2Ru_2O_7$ compounds, which yield information about the effect of A cations on electronic structure. For $Tl_2Ru_2O_7$, a peak-like feature in the mid-infrared (IR) region was observed in the optical conductivity spectra⁷, which shifts to low frequencies with decreasing temperature. For $Bi_2Ru_2O_7$, the mid-IR feature moves to low frequency region further and overlaps with a sharp Drude component. In contrast, no mid-IR feature was observed in optical spectra of insulator $Y_2Ru_2O_7$. Thus, it appears that the mid-IR feature is related to metallic nature of $A_2Ru_2O_7$. However, the origin of the mid-IR peak remains unclear. For $Tl_2Ru_2O_7$, the mid-IR peak is attributed to the interband transition between the lower Hubbard band(LHB) of Ru 4d t_{2g} energy level and the newly formed midgap state near the Fermi level caused by self-doping from Tl_2O to RuO_6 ⁷. For $Bi_2Ru_2O_7$, the electron-electron correlation is quite weak and its t_{2g} energy level could not split into LHB and UHB bands¹⁰. One may thus search for an alternative interpretation for metallic $A_2Ru_2O_7$.

$Pb_2Ru_2O_{7-\delta}$ is also a Pauli paramagnetic metal in the whole measured temperature range⁴. Among reported pyrochlore ruthenates, this compound has the least resistivity. Its resistivity decreases significantly with decreasing temperature, whereas the resistivity of $Bi_2Ru_2O_7$ keeps about $600\text{ }\mu\Omega\text{cm}$ in the temperature range between 10 to 300 K.⁵ High-resolution electron-energy-loss spectroscopy(HREELS) analysis⁸ shows that the density of states (DOS) at E_F of $Pb_2Ru_2O_{7-\delta}$ is higher than that of $Bi_2Ru_2O_7$. All the above experimental phenomena imply that $Pb_2Ru_2O_{7-\delta}$ is a better metal than $Bi_2Ru_2O_7$. In this work, we report the optical conductivity spectra of $Pb_2Ru_2O_{7-\delta}$ single crystal at different temperatures. At low frequencies, the optical spectra show typical Drude responses, but with a knee feature around 1000 cm^{-1} . Above 20000 cm^{-1} , a broad absorption feature is observed. Our analysis suggests that the low-frequency responses may be understood from two Drude compo-

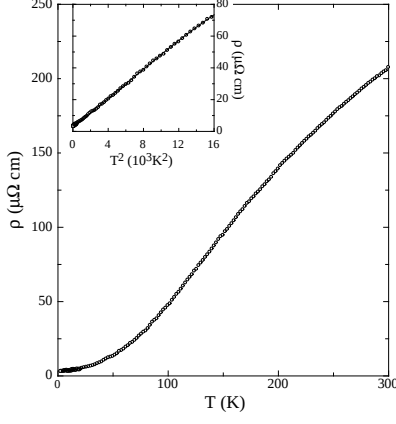


FIG. 1: Temperature dependence of the electrical resistivity ρ between 2 and 300 K. The inset is the plot of ρ vs. T^2 between 2 and 120 K. Note the linear behavior of ρ with T^2 .

nents arising from the partially filled Ru t_{2g} bands with different plasma frequencies and scattering rates. The high-frequency broad absorption may be due to interband transitions from occupied Ru t_{2g} states to empty e_g bands and from the occupied O 2p states to unoccupied Ru t_{2g} bands.

Single crystals of $Pb_2Ru_2O_{7-\delta}$ were grown using a vapor transport method described in detail elsewhere.¹¹ The temperature dependent resistivity measured by standard four probe method is shown in Fig. 1, which indicates a typical metallic behavior. The resistivity values are lower than the reported data,⁴ reflecting high quality of the crystal. We have measured the frequency dependent reflectivity $R(\omega)$ from 50 cm^{-1} to 30000 cm^{-1} at different temperatures. The measurements were performed on a Bruker 66v/s spectrometer with a He flowing cryostat. An *in-situ* overcoating technique is used for the reflectance measurement.¹² Standard Kramers-Kronig transformations are employed to derive the frequency-dependent optical conductivity.

Plotted in Fig. 2 is the reflectivity spectra at various temperatures. In low-frequency region, the reflectivity $R(\omega)$ slightly increases with decreasing temperature. At higher but below 8000 cm^{-1} frequency region, the reflectivity slightly decreases with decreasing temperature. $R(\omega)$ at different temperatures cross between 1000 cm^{-1} and 2000 cm^{-1} . A plasma edge minimum can be seen at frequency close to 13000 cm^{-1} .

Fig. 3 is a collection of the real part of the optical conductivity between 10 and 300 K. In the high frequency side, there is a broad interband transition peak at about 23000 cm^{-1} . Peaks at similar energies have been observed in $Bi_2Ru_2O_7$ and $Tl_2Ru_2O_7$, and were attributed to the interband transition from filled O 2p band to unoccupied Ru 4d t_{2g} band. Since the transition from occupied t_{2g} band to empty Ru e_g band is also close to this energy¹³, this broad feature may compose of both interband transitions. Below 13000 cm^{-1} , $\sigma_1(\omega)$ shows a Drude-like response, but with a knee feature near 1000 cm^{-1} . Its spec-

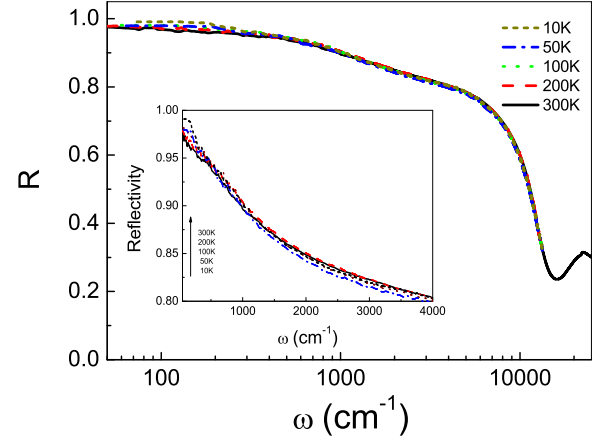


FIG. 2: The plot of frequency-dependent reflectivities at 300 K, 200 K, 100 K, 50 K and 10 K. Inset shows the low frequency data in an expanded scale.

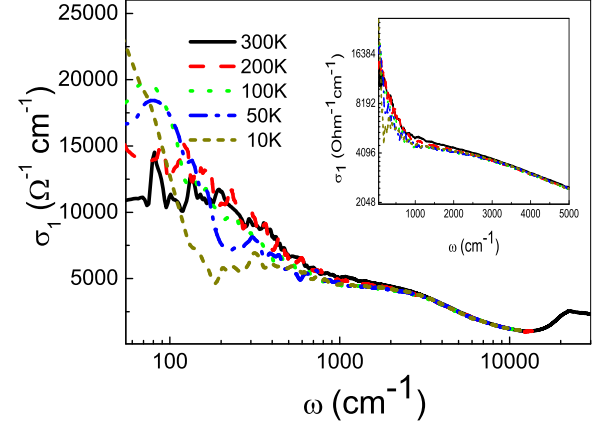


FIG. 3: The plot of frequency dependent conductivities at 300 K, 200 K, 100 K, 50 K and 10 K. Inset shows the low frequency data in an expanded scale.

tra weight at about 1000 cm^{-1} decreases slightly when temperature decreases. In $Bi_2Ru_2O_7$ ¹⁴, similar absorption feature at 292K is observed too, which is considered as a mid-IR peak of interband transition inherited from $Tl_2Ru_2O_7$.

The sum of the optical conductivity spectral weight gives a measure of the effective carrier number $\frac{m}{m^*}N_{eff}(\omega_c)$ of $Pb_2Ru_2O_{7-\delta}$:

$$\frac{m}{m^*}N_{eff}(\omega_c) = \frac{2m_0}{\pi e^2 N} \int_0^{\omega_c} \sigma(\omega) d\omega \quad (1)$$

in which m is the bare electron mass, m^*/m is the ratio of the effective mass to free electron mass, N is the number of Ru ions per unit volume and ω_c is a cutoff frequency. Assuming that $\omega_c = 1.5\text{eV}$ (about 12000 cm^{-1}) as for $Tl_2Ru_2O_7$ ⁷, we get $\frac{m}{m^*}N_{eff}(1.5\text{eV}) = 0.934$. This value is considerably higher than that of $Tl_2Ru_2O_7$. That is consistent with the fact that $Pb_2Ru_2O_{7-\delta}$ is more metallic than $Tl_2Ru_2O_7$.

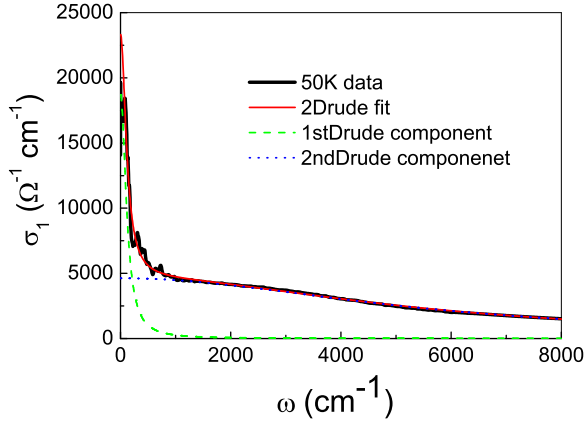


FIG. 4: Fitting with two Drude terms to the optical conductivity spectrum at 50K.

In optical conductivity spectra of $Tl_2Ru_2O_7$, there is a mid-IR peak centering at $4000cm^{-1}$.⁷ Band structure calculations¹ show that, antibonding states of Tl 6s and O(2) 2p lie in the energy range from -1eV to 2eV and partly hybridize with the Ru 4d (t_{2g})-O(1) 2p antibonding states. That will lead to net charge transfer from $Tl_2O(2)$ chain to the net-work of $RuO(1)_6$ octahedra. Such a charge transfer effect will generate some midgap states within the gap between up Hubbard band(UHB) and low Hubbard band(LHB).^{7,15}. When the midgap states lie above E_F and close to LHB, an interband transition between LHB and those midgap states is possible. Then a Lorentz-like peak appears in the optical conductivity spectra. The previous explanation of the mid-IR absorption feature seen in $Bi_2Ru_2O_7$ is on the similar basis, although it is considered that such self-doped state would be higher in metallic $Bi_2Ru_2O_7$ than that in $Tl_2Ru_2O_7$ ¹⁴.

For $Pb_2Ru_2O_{7-\delta}$, both the dc resistivity (see Fig.1) and the $N_{eff}(\omega_c)$ deduced from our optical conductivity spectra show that it is a much better metal than $Tl_2Ru_2O_7$. Band calculations also show that the band structures of $Bi_2Ru_2O_7$ and $Pb_2Ru_2O_{7-\delta}$ around E_F are quite different from that of $Tl_2Ru_2O_7$ due to different Ru-O-Ru angles and different ways of participation of A-cation orbits. The Ru-O-Ru angles in $Bi_2Ru_2O_7$ and $Pb_2Ru_2O_{7-\delta}$ are larger than that in $Tl_2Ru_2O_7$, leading to wider bandwidth of Ru 4d band for $Bi_2Ru_2O_7$ and $Pb_2Ru_2O_{7-\delta}$ by changing the corresponding hopping integrals. Since partial Bi and Pb 6p states situate near E_F and mix well with Ru t_{2g} states around E_F , the conducting electrons in $Bi_2Ru_2O_7$ and $Pb_2Ru_2O_{7-\delta}$ are more itinerant than that in $Tl_2Ru_2O_7$. Therefore, the on-site Coulomb interaction is relatively weak and the Hubbard bands merge into a single one¹⁰. In this case, the knee feature around $1000 cm^{-1}$ may not be attributed to the interband transition between LHB and the midgap states for $Pb_2Ru_2O_{7-\delta}$.

We note that the mid-IR feature for $Pb_2Ru_2O_{7-\delta}$ has its central frequency at zero, suggesting a Drude charac-

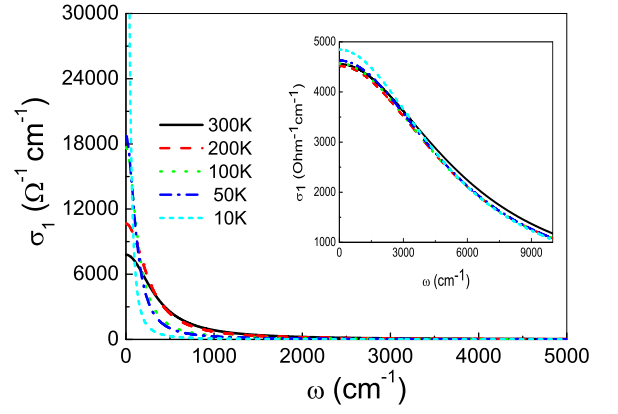


FIG. 5: The temperature dependences of 1st. Drude term and 2nd. Drude term (in the inset) of the fitting function

TABLE I: The parameters of function(2) at 300 K, 200 K, 100 K, 50 K and 10 K

$T(K)$	$\omega_{p,1}(cm^{-1})$	$\gamma_1(cm^{-1})$	$\omega_{p,2}(cm^{-1})$	$\gamma_2(cm^{-1})$
300K	12779	349	40169	5902
200K	13094	268	38983	5605
100K	12190	140	38975	5543
50K	11616	120	39160	5524
10K	12158	31	39123	5268

teristic. Then we may consider the low frequency part of the optical conductivity of $Pb_2Ru_2O_{7-\delta}$ as a sum of two kinds of intraband transitions, i.e.,

$$\sigma_1(\omega) = \frac{1}{4\pi} \frac{\omega_{p,1}^2 \cdot \gamma_1}{\omega^2 + \gamma_1^2} + \frac{1}{4\pi} \frac{\omega_{p,2}^2 \cdot \gamma_2}{\omega^2 + \gamma_2^2} \quad (2)$$

where $\omega_{p,1}$ and $\omega_{p,2}$ are the plasma frequencies, γ_1 and γ_2 are relaxation rates of the free charge carriers. We find that this function can well reproduce all the spectral data at all temperatures we have measured. The fitting parameters are listed in table.I.

Fig. 4 is the fitting result for spectral data at 50 K, where the thick solid line is the experimental data, the thin line is a fitting curve using function(2), the dashed line is the first Drude term and the dotted line is the second Drude term.

Presented in Fig. 5 is a plot of the fitting curves of the first Drude term at different temperatures. The inset displays those of second Drude term. Both of them show usual narrowings with decreasing temperature. Our fitting results imply that two kinds of conducting charge carriers with different lifetimes have taken part in the intraband excitations, and have different temperature dependencies. The carriers with smaller γ value have stronger temperature dependence, while another one is much weaker. The cooperation of the two different temperature-dependent behaviors leads to the decrease of the spectral weight around $1000cm^{-1}$ in the optical

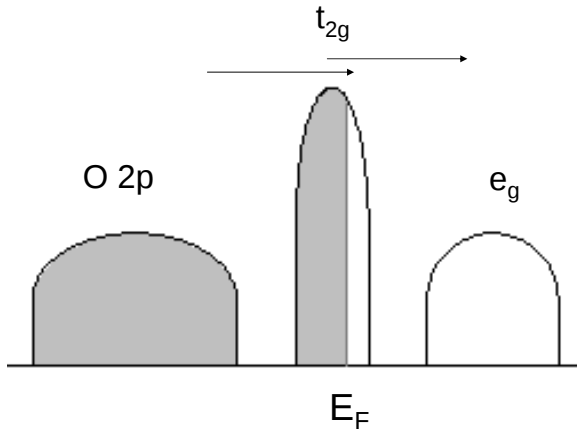


FIG. 6: A schematic picture of electronic states near E_F of $Pb_2Ru_2O_{7-\delta}$. The Ru 4d levels are split into t_{2g} and e_g bands. The partially occupied t_{2g} bands are hybridized with partial Pb 6p states. The filled O 2p bands are 2 eV away from the Fermi level.

conductivity spectra with decreasing temperature.

Our analysis is well consistent with the band-structure

calculation results.¹³ As displayed in Fig. 6, the fivefold degenerate Ru 4d levels are split, due to the octahedral crystal field, into an unoccupied e_g band which locate at 2 ~ 5 eV above E_F , and a partially occupied t_{2g} band between -1 and 1 eV. This t_{2g} band is broadened by mixing with some Pb 6p states. The O 2p bands locate between -7.5 eV and -2 eV.¹³ The broad feature at high frequencies (above 20000cm^{-1}) is contributed by two possible interband transitions with similar energy scales: from the occupied Ru t_{2g} bands to empty e_g bands and from the filled O 2p states to unoccupied Ru t_{2g} states. The low frequency part below the conductivity minimum is due to the intraband excitations of the two partially filled Ru t_{2g} bands. The existence of A-cation orbital near E_F actually leads to different band dispersions of the Ru t_{2g} bands.

This work is in part supported by National Science Foundation of China and Wang-Kuan-Cheng Foundation for research collaboration (R.J.). Oak Ridge National Laboratory is managed by UT-Battelle, LLC, for the U.S. Department of Energy under contract DE-AC05-00OR22725.

- ¹ F. Ishii and T. Oguchi, J. Phys. Soc. Jpn. **69**, 526 (2000).
- ² M. A. Subramanian, G. Aravamudan and G. V. Subba Rao, Pro. Solid State Chem. **15**, 55 (1983).
- ³ T. Takeda, M. Nagata, H. Kobayashi, R. Kanno, Y. Kawamoto, M. Takano, T. Kamiyama, F. Izumi and A. W. Sleight, J. Solid State Chem. **140**, 55 (1998).
- ⁴ H. Kobayashi, R. Kanno, Y. Kawamoto, T. Kamiyama, F. Izumi and A. W. Sleight, J. Solid State Chem. **114**, 15 (1995).
- ⁵ S. Yoshii and M. Sato, J. Phys. Soc. Jpn. **68**, 3034 (1999).
- ⁶ B. J. Kennedy, Physica B **241-243**, 303 (1998).
- ⁷ J. S. Lee, Y. S. Lee, K. W. Kim, T. W. Noh, Jaeyun Yu, T. Takeda and R. Kanno, Phys. Rev. B **64**, 165108 (2001).
- ⁸ P. A. Cox, R. G. Egdell, J. B. Goodenough, A. Hamnett and C. C. Naish, J. Phys.: Solid State Phys. **16**, 6221 (1983).

- ⁹ B. J. Kennedy and T. Vogt, J. Solid State Chem. **126**, 261 (1996).
- ¹⁰ J. S. Lee, Y. S. Lee, T. W. Noh, K. Char, Jonghyurk Park, S. -J. Oh, J. -H. Park, C. B. Eom, T. Takeda and R. Kanno, Phys. Rev. B **64**, 245107 (2001).
- ¹¹ R. Jin and D. Mandrus, unpublished.
- ¹² C. C. Homes, M. Reedyk, D. A. Crandles, and T. Timusk, Appl. Opt. **32**, 2973 (1993).
- ¹³ William Y. Hsu, Robert V. Kasowski, Thomas Miller and Tai-Chang Chiang, Appl. Phys. Lett. **52**, 792 (1988).
- ¹⁴ J. S. Lee, Y. S. Lee, K. W. Kim, T. W. Noh, J. Yu, Y. Takeda and R. Kannoo, Physica C **364-365**, 632 (2001).
- ¹⁵ M. B. J. Meinders, H. Eskes and G. A. Sawatzky, Phys. Rev. B **48**, 3916 (1993).